

# ARCURY® Series




ARCURY® AD



ARCURY® AL



ARCURY® SO

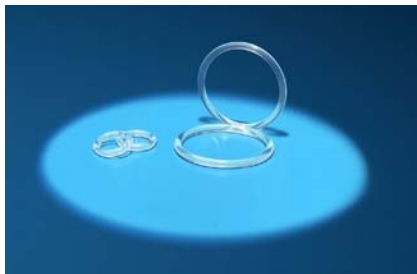

ARCURY® OZT



ARCURY® OZW

## Features and Typical Properties

Material Name	ARCURY® AD	ARCURY® AL	ARCURY® SO	ARCURY® OZT	ARCURY® OZW
Feature	Excellent resistance against acid Excellent purity (lowest extraction of metals and organics)	Excellent resistance against alkali solvent including ammonia	Excellent resistance against polar organic solvent including ketone, ester and amine	Excellent resistance against ozone gas and ozone water Excellent purity (lowest extraction of metals and organics)	Excellent resistance against ozone gas and ozone water Higher heat resistance
Color	Transparent Amber	Black	White	Transparent Clear	White
Hardness (Shore A)	67	75	73	60	68
Tensile Strength (MPa)	12.0	23.8	9.4	17.0	13.0
Elongation (%)	190	220	185	580	230
100% Modulus (MPa)	3.3	7.5	4.6	1.7	3.4
Compression Set (%)	25 <sup>1)</sup>	31 <sup>1)</sup>	16 <sup>2)</sup>	48 <sup>2)</sup>	37 <sup>1)</sup>
Main applications	1. Wafer and glass substrate cleaning equipment 2. Spin coater, Spin developer 3. Chemical carrier tank seal 4. Seals for Valves, Filters and Joints			1. Ozone cleaning machine 2. Ozone generation machine 3. Ozone decomposition machine	

<sup>1)</sup> 25% compression, 200°C x 72 hours, AS568A-214 O-ring    <sup>2)</sup> 25% compression, 150°C x 72 hours, AS568A-214 O-ring  
Above values are actual measurements, not standards.



# Chemical compatibilities

## ARCURY® AD

Chemical	Conditions	Swelling Ratio
Ultra pure water	80C, 30 days	0
Fluoric acid	25C, 30 days	0
HCl (36wt%):H <sub>2</sub> O <sub>2</sub> (30wt%):H <sub>2</sub> O = 1:1:5	80C, 168 hours	< 5%
H <sub>2</sub> SO <sub>4</sub> (98wt%):H <sub>2</sub> O <sub>2</sub> (30wt%) = 4:1	80C, 168 hours	< 5%
HF (50wt%):H <sub>2</sub> O <sub>2</sub> (30wt%):H <sub>2</sub> O = 1:1:100	23C, 168 hours	< 5%
HF (50wt%):H <sub>2</sub> O = 1:100	80C, 168 hours	< 5%
HF (47wt%):NH <sub>4</sub> F (40wt%) = 1:6	23C, 168 hours	< 5%
H <sub>3</sub> PO <sub>4</sub> (85wt%)	80C, 168 hours	< 5%

## ARCURY® AL

Chemical and Solvent	Conditions	Result	
		ARCURY®-AL	General FKM
NMP	80C, 168hrs	5.7%	300%
Ammonium Water (30%)	40C, 168hrs	1.6%	181%
Methyl Ethyl Ketone	R.T., 168HRS	>50%	>50%
Methanol	R.T., 168HRS	<5%	>50%
Ammonia Water (30%)	40C, 168HRS	<5%	>50%
Ethyl Acetate	R.T., 168HRS	>50%	>50%
Di-n-Buthyl Ether	R.T., 168HRS	20~50%	<5%
Sodium Hydroxide (50%)	40C, 168HRS	<5%	<5%
Hydrochloric Acid (35%)	40C, 168hrs	<5%	5~20%
Sulfuric Acid (97%)	40C, 168hrs	<5%	<5%
Nitric Acid (65%)	40C, 168hrs	<5%	20~50%
Acetic Acid	40C, 168hrs	20~50%	>50%
Fluoric Acid (46%)	40C, 168hrs	<5%	<5%
Hydrogen Peroxide (31%)	R.T., 168hrs	<5%	<5%

## ARCURY® SO

Chemical and Solvent	Conditions	Result	
		ARCURY®-SO	General FKM
Methyl Ethyl Ketone	R.T., 168hrs	15.8%	266%
Ethyl Acetate	R.T., 168hrs	17.7%	248%
Mono Ethanol Amine	80C, 168hrs	3%	(dissolved)
Methanol	R.T., 168hrs	<5%	>50%
Di-n-Buthyl Ether	R.T., 168hrs	>50%	<5%
Ammonia Water (30%)	40C, 168hrs	<5%	>50%
Sodium Hydroxide (50%)	40C, 168hrs	<5%	<5%
Hydrochloric Acid (35%)	40C, 168hrs	<5%	5~20%
Nitric Acid (65%)	40C, 168hrs	5~20%	20~50%
Acetic Acid	40C, 168hrs	5~20%	>50%
Fluoric Acid (46%)	40C, 168hrs	5~20%	<5%
Hydrogen Peroxide (31%)	R.T., 168hrs	<5%	<5%
NMP	80C, 168hrs	5~20%	>50%

All trademarks and registered trademarks noted in this file are the exclusive property of Nippon Valqua Industries, Ltd. unless otherwise specified. Although these data are created based on the data and the information (Internal master file No.: VMF104-011) as of March 2011, Nippon Valqua Industries, Ltd. may change these data without notice for the reason of improvement in functional of a product, standard revision and others. Please note the following point in use of these data. (1) An operating temperature, pressure range, durability, etc. indicated in this catalogue do not assume each operation conditions but show the application possibility based on our company data, an actual result, etc. Therefore, please use these data after checking the aptitude in actual use environment. (2) The data contained within this catalogue can only be taken as a guide. (3) A standard, a value, etc. are the purposes made legible, and may be performing an extract, recombination, arrangement, conversion, etc. of a value. (4) Although the maximum attention was paid in this data creation, Nippon Valqua Industries, Ltd. will not accept responsibility for any loss incurred through error or omission. Please contact your distributor or VALQUA group if you have any questions.

© 2011 Nippon Valqua Industries, Ltd. All rights reserved.  
Products manufactured in Japan, unless otherwise specified.



4655 Old Ironsides Dr., Suite 380  
Santa Clara, CA 95054  
Tel (408) 986-1425  
Fax (408) 986-1426  
www.valqua-america.com

Version: 110328